arXiv:cond-mat/9606139v1 18 Jun 1996

The Neutron Peak in the Interlayer Tunneling Model of High Temperature Superconductors

Lan Yin[a], Sudip Chakravarty[a], and Philip W. Anderson[b]
[a] *Department of Physics and Astronomy, University of California, Los Angeles, CA 90095*
[b] *Joseph Henry Laboratories of Physics, Princeton University, Princeton, NJ 08544*

(February 1, 2008)

Recent neutron scattering experiments in YBCO exhibit an unusual magnetic peak that appears only below the superconducting transition temperature. The experimental observations are explained within the context of the interlayer tunneling theory of high temperature superconductors.

PACS: 74.72.-h, 74.20-z, 74.25Ha

Many experimental observations in high temperature superconductors are commonly fit with a phenomenological model that derives from the original theory of Bardeen, Cooper and Schrieffer (BCS). The model has certain ingredients. It is characterized by a gap equation corresponding to a presumed symmetry of the order parameter, with an adjustable dimensionless coupling constant, or alternately an adjustable ratio of the gap to the superconducting transition temperature, and a given Fermi surface. Inherent in this description are the coherence factors that determine a number of interference processes unique to the BCS theory. Although a microscopic derivation of this effective model for the high temperature superconductors does not exist, the model is still used with a considerable degree of confidence. The main difficulties, to which we return below, are the unusual normal state properties of these materials and the enormously high transition temperatures, but there are many others. Such difficulties are extensively surveyed in the literature [1].

In the absence of a microscopic derivation, it is useful to ask if this phenomenological BCS model is unique and if an alternative phenomenological model exists that is capable of capturing features of these superconductors. One such physically motivated model was elaborated in a recent paper [2]. In the present paper we examine this model, called the interlayer tunneling model, to interpret the startling neutron scattering experiments in optimally doped YBCO [3].

These neutron scattering experiments are startling for a number of reasons. The experiments appear to have established that there are no sharp, or even broad, features in the magnetic excitation spectrum in the normal state. In contrast, the superconducting state exhibits a sharp magnetic feature that appears to be localized both in energy and momentum. It is located at an energy of 41 meV and near a wavevector $(\pi/a, \pi/a, \pi/c_b)$, where a is the lattice spacing of the square-planar CuO lattice, and c_b is the distance between the nearest-neighbor copper atoms within a bilayer. The intensity under the peak vanishes at the transition temperature, but its frequency softens very little.

In principle, there can be many explanations, and such explanations have been proposed [4]. None of these explanations are fully microscopic, nor are they fully consistent with some of the other prominent experimental observations in these materials. In particular, we draw attention to the fact that explanations that rely on forming *coherent* linear superpositions of the bilayer bands would also predict large splittings of the bands in certain regions of the Brillouin zone. Such splittings, studied extensively in experiments, are missing to a high degree of accuracy [5]. The argument that the observed bands are highly renormalized has little force. If the renormalization effects are so strong as to reduce the splitting to nearly zero, it is not meaningful to speak of a coherent superposition of states at the experimentally relevant temperatures.

The explanation we have to offer within the interlayer tunneling model is exceedingly simple and purely kinematic in origin. We also present illustrative but quantitative results to compare with experiments. The comparison shows that many of the features of the experiments are captured well. While many improvements can possibly be made, the kinematic aspects should survive future scrutiny.

The model Hamiltonian, motivated earlier [2], is that of a bilayer complex. Its generalization to many layers is straightforward and not essential for the present purpose. It is

$$\begin{aligned} H = & \sum_{\mathbf{k}\sigma i} \varepsilon_{\mathbf{k}} c^{\dagger}_{\mathbf{k}\sigma i} c_{\mathbf{k}\sigma i} \\ & - \sum_{\mathbf{q},\mathbf{k},\mathbf{k}',\sigma,\sigma',i} V_{\mathbf{q},\mathbf{k},\mathbf{k}'} c^{\dagger}_{\mathbf{k}\sigma i} c^{\dagger}_{-\mathbf{k}+\mathbf{q}\sigma' i} c_{-\mathbf{k}'+\mathbf{q}\sigma' i} c_{\mathbf{k}'\sigma i} \\ & - \sum_{\mathbf{q},\mathbf{k},\sigma,\sigma',i\neq j} T_J(\mathbf{q},\mathbf{k}) \left[c^{\dagger}_{\mathbf{k}\sigma i} c^{\dagger}_{-\mathbf{k}+\mathbf{q}\sigma' i} c_{-\mathbf{k}+\mathbf{q}\sigma' j} c_{\mathbf{k}\sigma j} + \text{h.c.} \right]. \end{aligned} \tag{1}$$

Here $i = 1, 2$ is the layer index. The fermion operators are labeled by the spin σ and the wavevector $\mathbf{k}$; V is the in-plane pairing interaction. The last term describes tunneling of pairs between the layers. Such a Hamiltonian should be understood from the point of view of an effective Hamiltonian, as emphasized recently [6]. It incorporates the unique feature of the interlayer mechanism, that tunneling occurs with conservation of transverse momentum $\mathbf{k}$. Therefore, the momentum sum in the T_J term is only over $\mathbf{k}$ and $\mathbf{q}$. Disorder between the layers is weak, and even disorder would not affect this crucial difference between the tunneling and interaction terms.

Only in the subspace in which both the states $(\mathbf{k}\uparrow)$ and $(-\mathbf{k}\downarrow)$ are both simultaneously occupied or unoccupied, is the following reduced Hamiltonian sufficient:

$$H_{\rm red}=\sum_{\mathbf{k}\sigma i}\varepsilon_{\mathbf{k}}c^{\dagger}_{\mathbf{k}\sigma i}c_{\mathbf{k}\sigma i}-\sum_{\mathbf{k},\mathbf{k}',i}V_{\mathbf{k},\mathbf{k}'}c^{\dagger}_{\mathbf{k}\uparrow i}c^{\dagger}_{-\mathbf{k}\downarrow i}c_{-\mathbf{k}'\downarrow i}c_{\mathbf{k}'\uparrow i}$$
$$-\sum_{\mathbf{k},i\neq j}T_J(\mathbf{k})\left[c^{\dagger}_{\mathbf{k}\uparrow i}c^{\dagger}_{-\mathbf{k}\downarrow i}c_{-\mathbf{k}\downarrow j}c_{\mathbf{k}\uparrow j}+\text{h.c.}\right]. \qquad (2)$$

This is because these are the only matrix elements that survive. It must be remembered that the actual Hamiltonian is H and that $H_{\rm red}$ is merely a convenient tool to calculate the matrix elements in the paired subspace. We do not anticipate that the Schrieffer zero-momentum pairing hypothesis will be necessarily as accurate in this case as in BCS, but it surely will be a guide.

An important feature is the absence of the single particle tunneling term from the Hamiltonian, which allows for a coherent superposition of the states of the layers that leads to a splitting, not observed in experiments. Therefore, such terms are not included in our model. Although the single particle tunneling term is absent, incoherence does not preclude a particle-hole two particle tunneling term [2,6], because the two particle term is generated by a second order virtual process and the question about coherence is irrelevant; the energy need not be conserved in a virtual process. However, this term does not appear to be crucially important for optimally doped materials (except, see later). For underdoped materials exhibiting "spin gap" phenomena [7], this neglected term can be quite important [8]. We also note that we shall treat the Fermion operators as ordinary anticommuting fermion operators. This can only be a crude approximation due to the non-Fermi liquid feature of the normal state. A possible improvement along the lines discussed earlier [6] is exceedingly complex.

The mean field treatment of the reduced Hamiltonian is straightforward [2] and leads to the gap equation:

$$\Delta_{\mathbf{k}}=\frac{1}{1-\chi_{\mathbf{k}}T_J(\mathbf{k})}\sum_{\mathbf{k}'}V_{\mathbf{k},\mathbf{k}'}\chi_{\mathbf{k}'}\Delta_{\mathbf{k}'}, \qquad (3)$$

where $\chi_{\mathbf{k}}=(\Delta_{\mathbf{k}}/2E_{\mathbf{k}})\tanh(E_{\mathbf{k}}/2T)$ is the pair susceptibility, with $E_{\mathbf{k}}=\sqrt{(\varepsilon_{\mathbf{k}}-\mu)^2+\Delta^2_{\mathbf{k}}}$. Here μ is the chemical potential. Note that, until now, we have not specified the symmetry of the in-plane pairing kernel. We shall now assume it to be of the symmetry $d_{x^2-y^2}$, $V_{\mathbf{k},\mathbf{k}'}=Vg_{\mathbf{k}}g_{\mathbf{k}'}$, where $g_{\mathbf{k}}=\frac{1}{2}\left[\cos(k_xa)-\cos(k_ya)\right]$.

Further specifications are necessary. The in-plane one electron dispersion is chosen to be $\varepsilon_{\mathbf{k}}=-2t\left[\cos(k_xa)+\cos(k_ya)\right]+4t'\cos(k_xa)\cos(k_ya)$. The quantitative calculations are carried out with a representative set of parameters appropriate to YBCO. These are $t=0.25$ eV, $t'=0.45t$, and $\mu=-0.315$ eV, corresponding to an open Fermi surface, with a band filling of 0.86. The quantity $T_J(\mathbf{k})$ was argued [2] to be $T_J(\mathbf{k})=(T_J/16)\left[\cos(k_xa)-\cos(k_ya)\right]^4$. The validity of this expression is now strengthened by detailed electronic structure calculations [9] for the single particle hopping matrix element $t_{\perp}(\mathbf{k})$.

The magnetic neutron scattering intensity is proportional to the imaginary part of the wavevector and the frequency dependent spin susceptibility $\chi(\mathbf{q},\omega)$, which for the above model is simply the expression:

$$\chi(\mathbf{q},\omega)=\sum_{\mathbf{k}}\left[\frac{A^{+}_{\mathbf{k},\mathbf{q}}F^{-}_{\mathbf{k},\mathbf{q}}}{\Omega^{1}_{\mathbf{k},\mathbf{q}}(\omega)}+\frac{A^{-}_{\mathbf{k},\mathbf{q}}(1-F^{+}_{\mathbf{k},\mathbf{q}})}{2}\left(\frac{1}{\Omega^{2+}_{\mathbf{k},\mathbf{q}}(\omega)}-\frac{1}{\Omega^{2-}_{\mathbf{k},\mathbf{q}}(\omega)}\right)\right], \qquad (4)$$

where

$$A^{\pm}_{\mathbf{k},\mathbf{q}}=\frac{1}{2}\left[1\pm\frac{(\varepsilon_{\mathbf{k}}-\mu)(\varepsilon_{\mathbf{k}+\mathbf{q}}-\mu)+\Delta_{\mathbf{k}}\Delta_{\mathbf{k}+\mathbf{q}}}{E_{\mathbf{k}}E_{\mathbf{k}+\mathbf{q}}}\right], \qquad (5)$$

$\Omega^{1}_{\mathbf{k},\mathbf{q}}(\omega)=\omega-(E_{\mathbf{k}+\mathbf{q}}-E_{\mathbf{k}})+i\delta$, $\Omega^{2\pm}_{\mathbf{k},\mathbf{q}}(\omega)=\omega\pm(E_{\mathbf{k}+\mathbf{q}}+E_{\mathbf{k}})+i\delta$, $F^{\pm}_{\mathbf{k},\mathbf{q}}=f(E_{\mathbf{k}+\mathbf{q}})\pm f(E_{\mathbf{k}})$, and $f(x)$ is the Fermi function.

Note that near $T=0$ only the A^{-} terms contribute, and these are negiligible unless $\Delta_{\mathbf{k}}$ and $\Delta_{\mathbf{k}+\mathbf{q}}$ are of opposite sign, as noted in Ref. [3]. In fact, nothing is observed for $q\approx 0$ or 2π, as expected, and the peak appears at $\mathbf{q}=(\pi/a,\pi/a)$, connecting two opposite-sign lobes of x^2-y^2. At higher temperatures, the A^{+} part is temperature dependent, but almost frequency independent function for experimentally relevant frequencies. The χ with the A^{+} term omitted will be denoted by $\bar{\chi}$. We shall first calculate the imaginary part of this susceptibility by restricting all wavevectors to be in the CuO-plane. Later, we shall discuss the dependence on the momentum transfer perpendicular to the plane.

At $T=0$, Im $\bar{\chi}$ is calculated by solving the gap equation for a set of T_J, and with $\lambda\equiv N(0)V=0.184$, where $N(0)$ is the density of states per spin at the Fermi energy ($V=0.2$ eV, $N(0)=0.92$). These are shown in Fig. 1. While the calculations show a peak at the threshold for $T_J\neq 0$, in the pure BCS case, $T_J=0$, the intensity is a step discontinuity at the threshold, and other excitonic enhancement mechanisms are necessary to produce a peak at the threshold.

For illustrative purposes the gap equation is solved at finite temperatures for $\lambda=0.184$ and for a fixed $T_J=0.075$ eV. No attempts were made to fit precisely the experimental data. The results are plotted in Fig. 2. We calculate the intensity under the peak and plot it as a function of temperature. The intensity was calculated by fitting a linear background at high energies. The results are shown in Fig. 3. The intensity falls off to zero as the

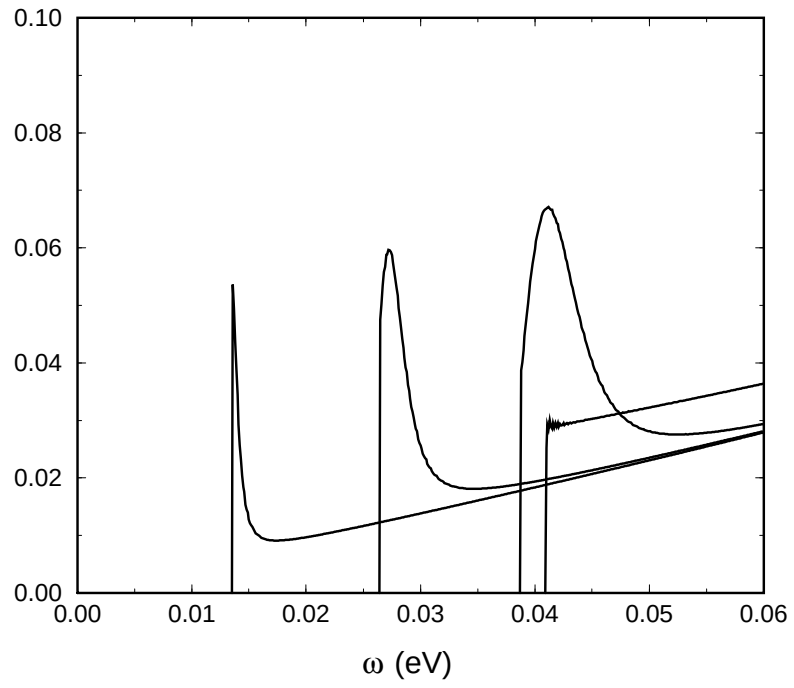

FIG. 1. Im $\bar{\chi}$ at $T = 0$. From left to right, T_J =0.025, 0.05, 0.075 eV. The curve corresponding to a step discontinuity at the edge is for BCS, with the maximum d-wave gap equal to 0.025 eV.

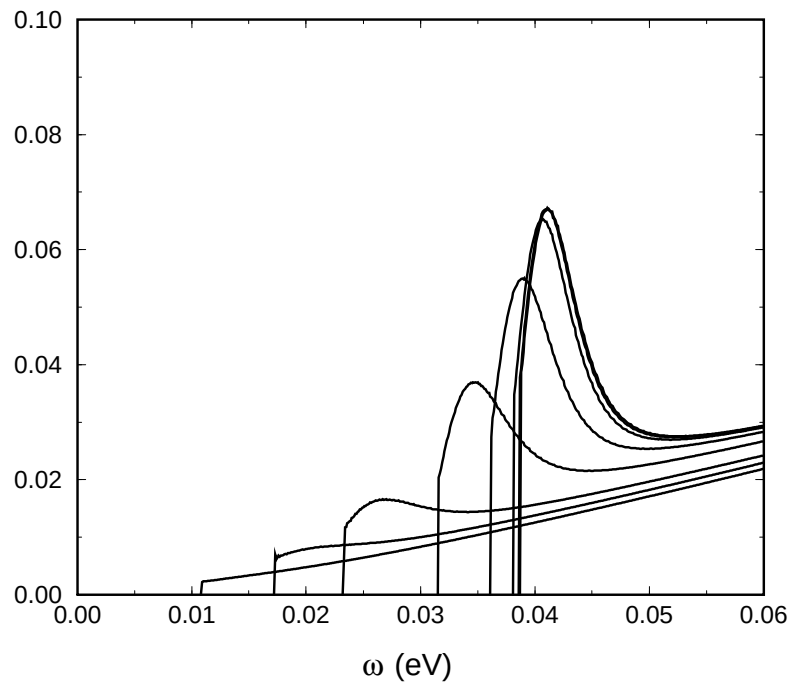

FIG. 2. Im $\bar{\chi}$ for $T_J = 0.075$ eV. From left to right, T =120, 110, 100, 80, 60, 40, 20, and 0 K. The results for $T = 0$ and 20 K are almost indistinguishable.

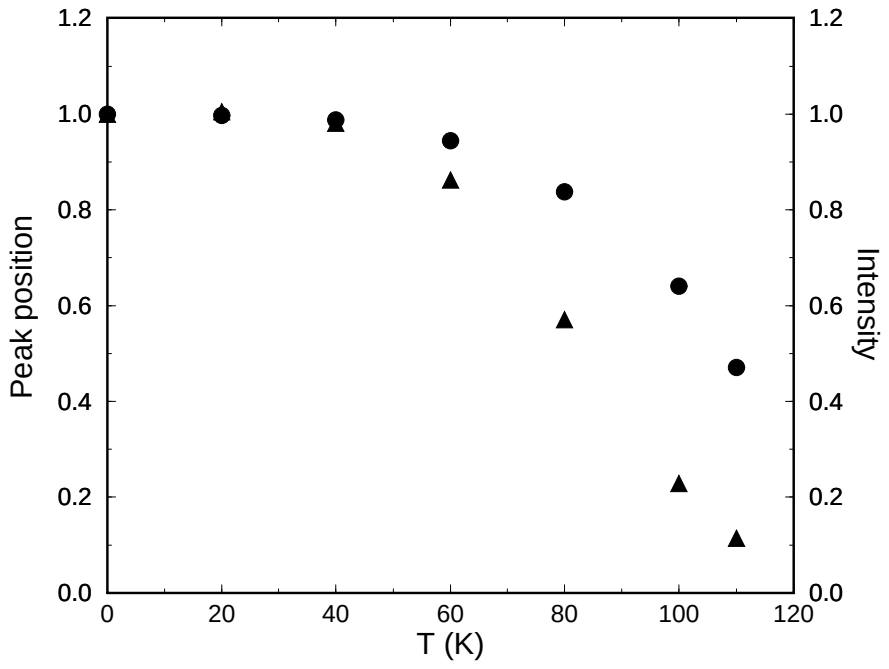

FIG. 3. The intensity (solid triangles) and the position of the peak (filled circles) normalized to the zero temperature values. The position of the peak is at 41.2 meV at $T = 0$.

temperature is raised to T_c and the results compare well with experiments. Also shown in Fig. 3, is the position of the peak, whose softening is weaker than the fall-off of the intensity. However, the experimental softening of the position of the peak is even weaker.

The question to address is why Im $\bar{\chi}$ produces a peak in the interlayer tunneling model, while the BCS model exhibits only a step discontinuity at the threshold. The reason is simple kinematics that holds for an open Fermi surface combined with an unusual feature of the interlayer gap equation. This feature was emphasized in early works on the gap equation [10], but has not been specifically noted in recent calculations: it is that when T_J dominates, as is necessarily so for high T_c, the density of states for a given value of $T_J/2$ is approximately a δ-function at $T_J/2$. Concomitant with this is the fact that electrons with $|\varepsilon_{\mathbf{k}} - \mu| > T_J(\mathbf{k})/2$ are unaffected by pairing, in contrast to BCS where effects of the gap extend out to high energies.

For simplicity, consider $T = 0$, set the coherence factor to unity and look at the wavevector $\mathbf{Q} = (\pi/a, \pi/a)$. In the BCS case, that is with $T_J(\mathbf{k})$ set equal to zero, $(E_{\mathbf{k}} + E_{\mathbf{Q+k}})$ has either minima, or saddle points. The minima give rise to a step discontinuity at the threshold at approximately twice the maximum of the d-wave gap (See Fig. 1.). The saddle points give rise to van Hove singularities which are generally not at the threshold, but can be brought close to the threshold by adjusting parameters.

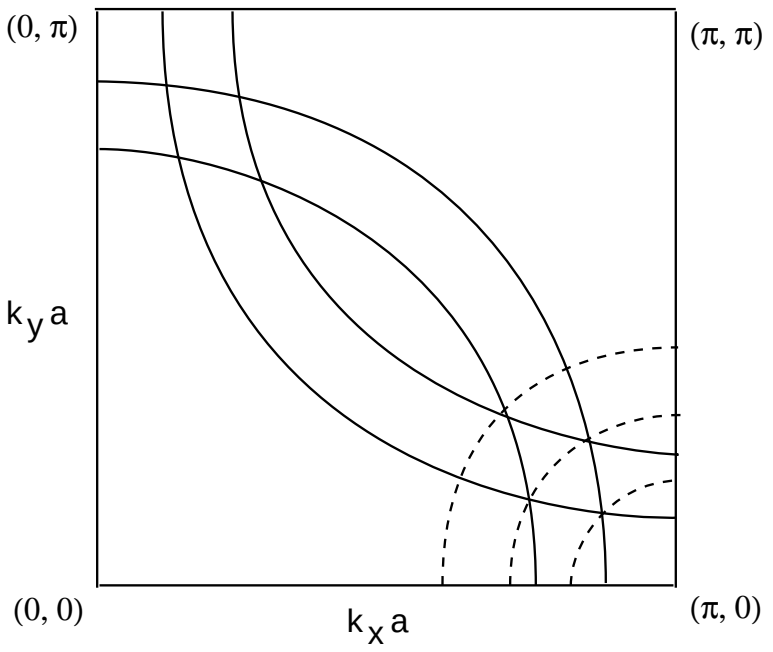

FIG. 4. The superconducting region and its mapping under $\mathbf{k} \rightarrow \mathbf{Q} - \mathbf{k}$. The diamond shaped overlap regions contribute to the peak of the imaginary part of the spin susceptibility. The dashed arcs are the constant ω-contours centered at $(\pi, 0)$.

Now consider the case of very small in-plane pairing kernel in the interlayer tunneling equation. The unusual feature is that the superconducting region is a very narrow region around the Fermi line as shown in Fig. 4. The scattering surface is now radically different. The contribution to the peak must come from regions in which both $\Delta_{\mathbf{k}}$ and $\Delta_{\mathbf{k+Q}}$ are finite. Also, note that $E_{\mathbf{k+Q}} = E_{\mathbf{Q-k}}$. The image of the superconducting region including the Fermi line under the mapping $\mathbf{k} \rightarrow \mathbf{Q} - \mathbf{k}$ is shown in Fig. 4. The regions in which both $\Delta_{\mathbf{k}}$ and $\Delta_{\mathbf{Q-k}}$ are finite are the diamond shaped overlap regions, with one of its diagonals given by $k_x + k_y = \pi$. Consider the lower diamond. In this region, we can write $E_{\mathbf{k}} \approx T_J \cos^4(d/\sqrt{2})$, where d is the distance from $(\pi/a, 0)$. The corresponding constant ω-contours are the arcs shown in Fig. 4.

Note that the Im $\bar{\chi}$, as a function of ω, is proportional to the length of the arcs for which $(E_{\mathbf{k}}+E_{\mathbf{Q}-\mathbf{k}}) = \omega$. The lower and the upper cutoffs are defined by the arcs touching the diamond, and the peak is contained between these two cutoffs. As ω increases, the arc length increases approximately linearly within the diamond, and then drops approximately linearly. Moreover, because the superconducting region around the Fermi line is very narrow, the width of this peak is also very narrow, as in experiments. The peak is at $T_J(\mathbf{k}_0)$, where $\mathbf{k}_0$ is located at the center of the diamond. This elementary analysis substantiates the numerical results in which none of the above simplifying approximations were made.

To understand the dependence of the scattering intensity on the momentum transfer perpendicular to the plane, it is necessary to consider the mixing of the electronic wavefunctions between the layers. This cannot be a coherent superposition of states, otherwise the bands will be split, which, as stated earlier, is not observed in experiments. However, a virtual mixing of the states due to second order processes, similar to superexchange, is possible. This virtual mixing can be described by approximately constructing the operators [8]: $\alpha_{\mathbf{k},\sigma,1} = (c_{\mathbf{k},\sigma,1} + \eta(\mathbf{k})c_{\mathbf{k},\sigma,2})/\sqrt{1+\eta^2(\mathbf{k})}$, and $\alpha_{\mathbf{k},\sigma,2} = (c_{\mathbf{k},\sigma,2} + \eta(\mathbf{k})c_{\mathbf{k},\sigma,1})/\sqrt{1+\eta^2(\mathbf{k})}$, where $\eta(\mathbf{k})$ is the mixing parameter. The order parameter that takes the mixing into account is $\Lambda_{\mathbf{k}} = \langle \alpha^\dagger_{\mathbf{k},\uparrow,1}\alpha^\dagger_{-\mathbf{k},\downarrow,1} + \alpha^\dagger_{\mathbf{k},\uparrow,2}\alpha^\dagger_{-\mathbf{k},\downarrow,2}\rangle$. It is also possible to rewrite this in terms of the operators $c^{\mathrm{e}}_{\mathbf{k},\sigma} = \frac{1}{\sqrt{2}}(c_{\mathbf{k},\sigma,1} + c_{\mathbf{k},\sigma,2})$ and $c^{\mathrm{o}}_{\mathbf{k},\sigma} = \frac{1}{\sqrt{2}}(c_{\mathbf{k},\sigma,1} - c_{\mathbf{k},\sigma,2})$. Thus,

$$\Lambda_{\mathbf{k}} = \frac{(1+\eta(\mathbf{k}))^2}{1+\eta^2(\mathbf{k})}\langle c^{\mathrm{e}\dagger}c^{-\mathrm{e}\dagger}\rangle + \frac{(1-\eta(\mathbf{k}))^2}{1+\eta^2(\mathbf{k})}\langle c^{\mathrm{o}\dagger}c^{-\mathrm{o}\dagger}\rangle, \quad (6)$$

where we have used the notation $c^{\mathrm{e}\dagger} \equiv c^{\mathrm{e}\dagger}_{\mathbf{k},\uparrow}$, $c^{-\mathrm{e}\dagger} \equiv c^{\mathrm{e}\dagger}_{-\mathbf{k},\downarrow}$, etc.

This virtual mixing of the wave functions on the layers is a necessary concomitant of the source of the pairing energy in the hopping terms in the original Hamiltonian $-\sum_{\mathbf{k},\sigma,i\neq j} t_\perp(\mathbf{k})(c^\dagger_{\mathbf{k},\sigma,i}c_{\mathbf{k},\sigma,j} + \mathrm{h.c.}) = -\sum_{\mathbf{k},\sigma} t_\perp(\mathbf{k})(n^{\mathrm{e}}_{\mathbf{k},\sigma} - n^{\mathrm{o}}_{\mathbf{k},\sigma})$, where n are the number operators. The pairing energy must be numerically augmented by its expectation value. However, the two-particle tunneling term alone does not give quite enough difference in occupancy to explain the experimental modulation with q_z. In a forthcoming paper [8], we will show that this tendency is strongly enhanced by including the "superexchange" type terms caused by virtual particle-hole hopping. In fact, it may be that the pairing occurs primarily in the "even" linear combination alone [11].

Then, any electron excited from the condensate must leave behind a hole in the even state. Similarly, it can accept only an electron in the odd state, hence the striking even ↔ odd selection rule observed in the neutron scattering experiments. Note that although the odd states are nominally unpaired, the addition or removal of an electron from the odd state destroys the pairing criterion and costs one unit of pairing energy. Thus, there is a gap for all one-electron excitations, even though only the even state is paired.

In conclusion, we find that these neutron results give us a surprisingly direct and complete picture of the nature of the pairing responsible for superconductivity, not only showing us the symmetry and approximate form of the energy gap, but even fixing the nature of the gap equation and the source of the pairing energy. In particular, the strong correlation between the layers excludes any purely intralayer mechanism for superconductivity, under our assumption — the singlet, and very plausible on other grounds — that the quasiparticle pairs do not have strong final state interactions.

This work was supported by the National Science Foundation: Grant Nos. DMR-9531575 and DMR-9104873. We thank B. Keimer for many stimulating discussions.

---

[1] P. W. Anderson, Science **256**, 1526 (1992).

[2] S. Chakravarty, A. Sudbø, P. W. Anderson, and S. Strong, Science **261**, 337 (1993).

[3] H. F. Fong *et al.*, Phys. Rev. Lett. **75**, 321 (1995) and H. F. Fong *et al.*, to be published.

[4] I. I. Mazin and V. Yakovenko, Phys. Rev. Lett. **75**, 4134 (1995); E. Delmer and S. -C. Zhang, Phys. Rev. Lett. **75**, 4126 (1995); D. Z. Liu, Y. Zha, and K. Levin, Phys. Rev. Lett. **75**, 4130 (1995); N. Bulut and D. J. Scalapino, Phys. Rev. B **53**, 5149 (1996); B. Normand, H. Kohno and H. Fukuyama, J. Phys. Jpn. **64**, 3903 (1995).

[5] H. Ding *et al.*, Phys. Rev. Lett. **76**, 1533 (1996); D. Van der Marel *et al.* Physica C **235-240**, 1145 (1994) and references therein.

[6] L. Yin and S. Chakravarty, Int. J. Mod. Phys. **10**, 805 (1996).

[7] A. G. Loeser *et al.*, Science, in press, H. Ding *et al.*, Nature, in press, and references therein.

[8] P.W. Anderson, preprint, in preparation.

[9] A. I. Liechtenstein, O. Gunnarsson, O. K. Andersen, and R. M. Martin, preprint (cond-mat/9509101).

[10] P. W. Anderson, Physica C **185-189**, 11 (1991); J. Phys. Chem. Solids **54**, 1073 (1993); Chapter VII of a forthcoming book.

[11] If we augment our Hamiltonian (Eq. 2) with an equal particle-hole pair hopping (superexchange) term and ignore the small in-plane interaction, it acquires an additional approximate symmetry with respect to the interchange of particles of a given spin species and of wave vector **k** between the layers. The odd order parameter does not respect this symmetry and must vanish unless the symmetry is spontaneously broken.